

Self-Powered Fast-Response X-Ray Detectors Based on Vertical GaN p-n Diodes

Leidang Zhou^{ID}, Xing Lu^{ID}, *Member, IEEE*, Jin Wu, Huaxing Jiang^{ID}, *Member, IEEE*, Liang Chen, Xiaoping Ouyang, and Kei May Lau^{ID}, *Fellow, IEEE*

Abstract—GaN offers an excellent potential for fabricating X-ray detectors, taking advantage of its superior material properties and well-developed manufacturing technologies. In this letter, we demonstrated a self-powered fast-response X-ray detection using GaN-based vertical p-n diodes grown on a bulk GaN substrate. Attributed to the high crystalline quality achieved by homoepitaxy, the fabricated photodiodes exhibited an excellent rectification behavior, and therefore, a strong photovoltaic response to X-ray illumination when biased at 0 V. The transient X-ray detection analysis revealed that the self-powered detectors have a relatively short response time (< 20 ms) and a good linear response to the X-ray incident dose rate with a high specific sensitivity of $170 \text{ nC}\cdot\text{Gy}^{-1}\cdot\text{cm}^{-2}$.

Index Terms—GaN, p-n diode, self-powered, X-ray detectors.

I. INTRODUCTION

DIRECT-CONVERSION semiconductor X-ray detectors have received remarkable research interests in recent years because of their superior properties, such as high energy resolution, small system volume, low cost, and suitability for mass production. They can benefit a range of applications including medical diagnostics, security systems, and aerospace and nuclear industries [1]–[4]. To obtain a reasonable detectivity, the X-ray detectors generally require a relatively large size external power supply, which makes the overall circuitry bulky and uneconomical in the current low-carbon scenario [5], [6]. Thus, X-ray detectors which are able to detect at a zero-volt bias, namely self-powered, can be an energy-efficient solution [7]–[9].

Manuscript received April 20, 2019; accepted April 29, 2019. Date of publication May 3, 2019; date of current version June 26, 2019. This work was supported in part by the Frontier and Key Technological Innovation Foundation of Guangdong Province under Grant 2017A050506039 and in part by the International Science and Technology Cooperation Program of Guangzhou under Grant 201807010093. The review of this letter was arranged by Editor G. Han. (Corresponding author: Xing Lu.)

L. Zhou is with the School of Microelectronics, Xi'an Jiaotong University, Xi'an 710049, China.

X. Lu and J. Wu are with the State Key Laboratory of Optoelectronic Materials and Technologies, School of Electronics and Information Technology, Sun Yat-sen University, Guangzhou 510275, China (e-mail: lux86@mail.sysu.edu.cn).

H. Jiang and K. M. Lau are with the Department of Electronic and Computer Engineering, The Hong Kong University of Science and Technology, Hong Kong.

L. Chen and X. Ouyang are with the Radiation Detection Research Center, Northwest Institute of Nuclear Technology, Xi'an 710024, China.

Color versions of one or more of the figures in this letter are available online at <http://ieeexplore.ieee.org>.

Digital Object Identifier 10.1109/LED.2019.2914585

GaN is a commercial semiconductor that has been extensively used for both optoelectronic and electronic devices [10], such as light-emitting diodes (LEDs) [11], laser diodes (LDs) [12], photodetectors [13], sensors [14] and high-speed high-power field-effect transistors (FETs) [15]–[17]. The wide bandgap (4.3 eV), large density ($6.09 \text{ g}\cdot\text{cm}^{-3}$), relatively large atomic number of Ga (31) and excellent chemical and thermal stability also make GaN a promising candidate for X-ray and particle detection [18]–[24], particularly in high temperature and radiation environments. The availability of high quality bulk GaN substrate enables the fabrication of high performance vertical GaN radiation detectors, since a much thicker sensitive region is essential to collect the high-energy radiation photons and charged particles. Furthermore, GaN-based detectors can be potentially integrated with a wide range of well-developed GaN-based electronics and circuits to yield a compact radiation detection system [25]–[28].

In this letter, GaN-based vertical p-n diodes have been fabricated on a bulk GaN substrate and tested as X-ray detectors. The device exhibited a low reverse leakage current density of $\sim 10^{-1} \text{ A}/\text{cm}^2$ at -300 V . When biased at 0 V, the detector showed a fast and stable transient response to the switching of X-ray illumination using internal photovoltaic effect, demonstrating the great potential of using GaN p-n diodes as self-powered X-ray detectors or X-ray photocells.

II. EXPERIMENTS

The GaN p-n structure used in this study was grown on a 2-inch bulk GaN substrate by metal organic chemical vapor deposition (MOCVD). The n-type GaN substrate was of $350 \mu\text{m}$ thick, with a resistivity of $\sim 0.05 \Omega\cdot\text{cm}$ and a dislocation density of $\sim 5 \times 10^5 \text{ cm}^{-2}$. The epilayers included a 200-nm thick Si-doped n^+ -GaN layer ($\sim n = 2 \times 10^{18} \text{ cm}^{-3}$), a 5- μm thick unintentionally doped n^- -GaN layer (carrier concentration at the order of 10^{16} cm^{-3}), and a 500-nm Mg-doped p-type GaN ($\sim p = 2 \times 10^{17} \text{ cm}^{-3}$). Trimethylgallium (TMGa) and ammonia (NH_3) were used as precursors for Ga and N, respectively. Fig. 1(a) shows the atomic force microscopy (AFM) image of the as-grown sample. The root mean square (RMS) roughness was slightly high, 1.9 nm for a scanned area of $10 \times 10 \mu\text{m}^2$, which could be related to the low temperature growth of the upmost p-GaN layer. The fabrication of the vertical p-n diodes started with mesa isolation etching using a BCl_3/Cl_2 -based inductively coupled plasma (ICP) etch process. Following that, the sample was immersed into a 25% tetramethylammonium hydroxide (TMAH) solution

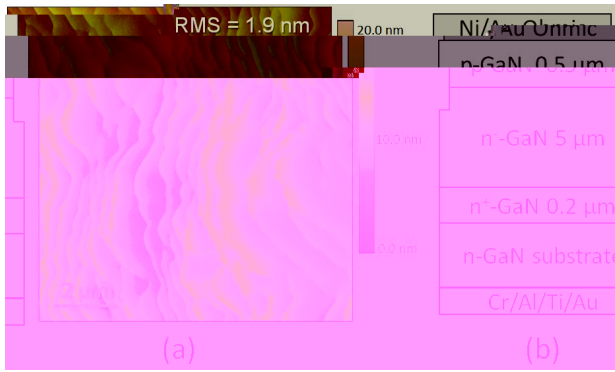


Fig. 1. (a) AFM image of the as-grown GaN p-n structure ON a bulk substrate. (b) Schematic cross-section of the vertical GaN p-n diode.

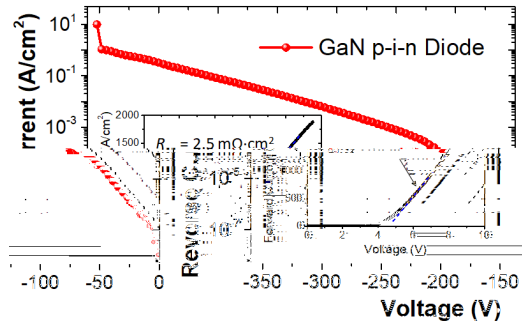


Fig. 2. Reverse I-V characteristics of the vertical GaN p-n diode. The inset shows the forward current of the device.

at 75 °C for 60 minutes. The TMAH treatment was found effective in suppression of leakage current by removing etch damages from the mesa sidewall [29]. Then, the p-electrode was formed by e-beam evaporation of a Ni/Au (30/30 nm) metal stack and a liftoff process. A rapid thermal annealing (RTA) at 570 °C was performed in an atmospheric ambient for 5 minutes to facilitate the formation of a good Ohmic contact between Ni and p-GaN. Subsequently, a Cr/Al/Ti/Au metal stack was deposited on the backside of the sample by e-beam evaporation, serving as n-electrode. Fig. 1(b) shows the cross-sectional schematic of the fabricated vertical GaN p-n diode. The diode was in circular shape with a diameter of 560 μm .

III. RESULTS AND DISCUSSION

Fig. 2 shows the reverse current-voltage (I - V) characteristics of the fabricated vertical GaN p-n diode in dark condition, with a breakdown voltage (V_{br}) of ~ 350 V. The reverse leakage current density of the vertical GaN p-n diode at -300 V is $\sim 10^{-1}$ A/cm 2 . The forward I - V characteristics of the device was shown in the inset of Fig. 2. The turn-on voltage (V_{ON}) extracted at the current density of 10 A/cm 2 was 3.8 V, close to the bandgap of GaN. The high V_{ON} and low leakage current correspond to a high barrier height, i.e. a high built-in potential in the p-n junction, which is essential for a self-powered photodetector using photovoltaic effect. A larger built-in electric field will provide better separation of photo-excited electron-hole pairs. Moreover, the fabricated diode exhibited a low on-state resistance (R_{ON}) of 2.5 m $\Omega\cdot\text{cm}^2$, indicating a greatly suppressed parasitic resistance in the device.

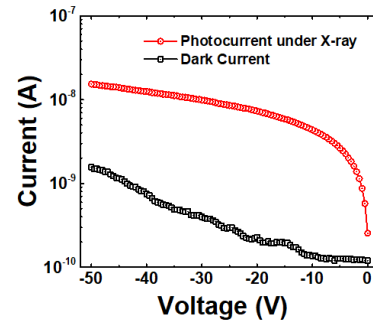


Fig. 3. Comparison of the photocurrent and dark current of the GaN p-n diode to X-ray illumination as a function of reverse bias voltage.

The fabricated diodes were mounted onto a conductive holder and wire bonded for the X-ray detection tests. A miniature X-ray source (60 kV, 12 W X-ray source, Moxtek, USA) was used in the experiments. When the X-ray tube accelerating voltage is set at 30 kV, a wide continuous spectrum of X-ray beam with a peak photon energy at around 24 keV can be generated. According to the calibration using a commercial Si X-ray detector, the X-ray dose rate at a distance of 1 cm from the source is 1.532 Gy/s when the X-ray tube current is set at 100 μA . The X-ray flux is proportional to the X-ray tube current, which can be tuned from 1 μA to 400 μA , when its accelerating voltage is fixed. All the X-ray detection measurements were conducted at RT in this study, and the detector was illuminated by X-ray from the front side perpendicularly with a distance to the X-ray source of 1 cm.

In order to demonstrate the X-ray detection capability, the reverse I - V characterization of the fabricated diode was performed under X-ray exposure with an incident dose rate of 1.532 Gy/s. As shown in Fig. 3, the photocurrent (I_p) of the GaN p-n detector increases dramatically when compared with its dark current (I_d).

The transient response of the GaN p-n detector to the switching of X-ray illumination was characterized and plotted in Fig. 4(a). The X-ray switching period was set to be 60 s, and the sampling frequency of the measurement was 50 Hz. When biased at 0 V, the detector exhibited a good and stable transient response. The dark current of the detector was well below the measurement limit of the equipment owing to its passive operation mode, which is one of the important advantages in terms of signal-to-noise ratio (SNR) and power consumption. Fig. 4(b) shows the enlarged plot of the rise and decay process of the photocurrent for the GaN p-n detector when the X-ray source was turned on and off. The switching time of the X-ray source is negligible. Both the rise time (t_r , 10% to 90%) and decay time (t_d , 90% to 10%) of the transient photocurrent were very short (< 20 ms, the time resolution of the equipment in our experiments). The result was benchmarked with other reported X-ray detectors in the literature using different wide bandgap semiconductors, as listed in Table I. Our device exhibited a competitively fast response speed, which could be attributed to the high built-in electric field within the GaN p-n junction. According to photovoltaic mechanism, electron-hole pairs were excited by the X-ray photons in the space-charge region of the zero-volt

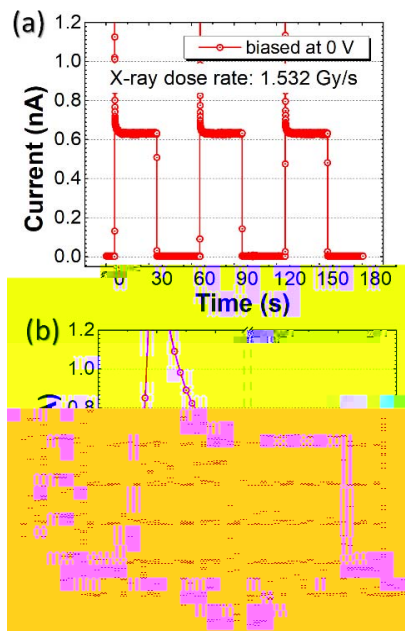


Fig. 4. (a) The transient responses of the GaN p-n detector to the switching of X-ray illumination at biases of 0 V. (b) The enlarged plots of the rise and decay process of the photocurrent when the X-ray source was turned on and OFF.

TABLE I
BENCHMARK OF RESPONSE SPEED OF THE WBG
SEMICONDUCTOR X-RAY DETECTORS

- [6] D. M. Trucchi, P. Allegrini, P. Calvani, A. Galbiati, K. Oliver, and G. Conte, Very fast and primingless single-crystal-diamond X-ray dosimeters, *IEEE Electron Device Lett.*, vol. 33, no. 4, pp. 615–617, Apr. 2012. doi: [10.1109/LED.2012.2185476](https://doi.org/10.1109/LED.2012.2185476).
- [7] Z. Gao, N. M. S. Jahed, and S. Sivoththaman, Large area self-powered Al-ZnO/(n)Si hetero-junction photodetectors with high responsivity, *IEEE Photon. Technol. Lett.*, vol. 29, no. 14, pp. 1171–1174, Jul. 15, 2017. doi: [10.1109/LPT.2017.2711485](https://doi.org/10.1109/LPT.2017.2711485).
- [8] A. I. Nusir and M. O. Manasreh, Self-powered near-infrared photodetector based on asymmetrical Schottky interdigital contacts, *IEEE Electron Device Lett.*, vol. 36, no. 11, pp. 1172–1175, Nov. 2015. doi: [10.1109/LED.2015.2478395](https://doi.org/10.1109/LED.2015.2478395).
- [9] H. Chen, K. Liu, L. Hu, A. A. Al-Ghamdi, and X. Fang, New concept ultraviolet photodetectors, *Mater. Today*, vol. 18, no. 9, pp. 493–502, Nov. 2015. doi: [10.1016/j.mattod.2015.06.001](https://doi.org/10.1016/j.mattod.2015.06.001).
- [10] R. F. Davis, III V nitrides for electronic and optoelectronic applications, *Proc. IEEE*, vol. 79, no. 5, pp. 702–712, May 1991. doi: [10.1109/5.90133](https://doi.org/10.1109/5.90133).
- [11] S. Pimpitkar, J. S. Speck, S. P. DenBaars, and S. Nakamura, Prospects for LED lighting, *Nature Photon.*, vol. 3, no. 4, pp. 180–182, Apr. 2009. doi: [10.1038/nphoton.2009.32](https://doi.org/10.1038/nphoton.2009.32).
- [12] S. Nakamura, M. Senoh, S.-I. Nagahama, N. Iwasa, T. Matsushita, and T. Mukai, Blue InGaP-based laser diodes with an emission wavelength of 450 nm, *Appl. Phys. Lett.*, vol. 76, no. 1, pp. 22–24, 1999. doi: [10.1063/1.125643](https://doi.org/10.1063/1.125643).
- [13] M. A. Khan, J. N. Kuznia, D. T. Olson, J. M. Van Hove, M. Blasingame, and L. F. Reitz, High-responsivity photoconductive ultraviolet sensors based on insulating single-crystal GaN epilayers, *Appl. Phys. Lett.*, vol. 60, no. 23, pp. 2917–2919, Jun. 1992.
- [14] X. Lu, C. M. Lee, S. Y. Wu, H. P. Ho, and K. M. Lau, GaN-based S_0 wave sensors on silicon for chemical and biological sensing in liquid environments, *IEEE Sensors J.*, vol. 13, no. 4, pp. 1245–1251, Apr. 2013. doi: [10.1109/JSEN.2012.2231958](https://doi.org/10.1109/JSEN.2012.2231958).
- [15] X. Lu, K. Yu, H. Jiang, A. Zhang, and K. M. Lau, Study of interface traps in AlGaP/GaN MISHEMTs using LPCVD SiN_x as gate dielectric, *IEEE Trans. Electron. Devices*, vol. 64, no. 3, pp. 824–831, Mar. 2017. doi: [10.1109/TED.2017.2654358](https://doi.org/10.1109/TED.2017.2654358).
- [16] U. K. Mishra, L. Shen, T. E. Kazior, and Y.-F. Wu, GaN-based RF power devices and amplifiers, *Proc. IEEE*, vol. 96, no. 2, pp. 287–305, Feb. 2008. doi: [10.1109/JPROC.2007.911060](https://doi.org/10.1109/JPROC.2007.911060).
- [17] X. Lu, J. Ma, H. Jiang, C. Liu, P. Xu, and K. M. Lau, Fabrication and characterization of gate-last self-aligned AlN/GaN MISHEMTs with *in situ* SiN_x gate dielectric, *IEEE Trans. Electron. Devices*, vol. 62, no. 6, pp. 1862–1869, Jun. 2015. doi: [10.1109/TED.2015.2421031](https://doi.org/10.1109/TED.2015.2421031).
- [18] J. Grant, R. Bates, W. Cunningham, A. Blue, J. Melone, F. McEwan, J. Vaitkus, E. Gaubas, and V. O'Shea, GaN as a radiation hard particle detector, *Nucl. Instrum. Methods Phys. Res. A, Accel. Spectrom. Detect. Assoc. Equip.*, vol. 576, no. 1, pp. 60–65, Jun. 2007. doi: [10.1016/j.nima.2007.01.121](https://doi.org/10.1016/j.nima.2007.01.121).
- [19] J. Y. Duboz, E. Frayssinet, S. Chenot, J. L. Reverchon, and M. Idir, X-ray detectors based on GaN, *Proc. SPIE*, vol. 8625, Mar. 2013, Art. no. 86251W. doi: [10.1117/12.2007827](https://doi.org/10.1117/12.2007827).
- [20] J.-Y. Duboz, M. La gte, D. Schenk, B. Beaumont, J.-L. Reverchon, A. D. Wieck, and T. Zimmerling, GaN for X-ray detection, *Appl. Phys. Lett.*, vol. 92, no. 26, 2008, Art. no. 263501. doi: [10.1063/1.2951619](https://doi.org/10.1063/1.2951619).
- [21] C. Yao, K. Fu, G. Wang, G. Yu, and M. Lu, GaN-based p-i-n X-ray detection, *Phys. Status Solidi A*, vol. 209, no. 1, pp. 204–206, 2012. doi: [10.1002/pssa.201127446](https://doi.org/10.1002/pssa.201127446).
- [22] A. Owens, M. Bavdaz, A. Peacock, A. Poelaert, H. Andersson, S. Nenonen, L. Tr ger, and G. Bertuccio, Hard X-ray spectroscopy using small format GaAs arrays, *Nucl. Instrum. Methods Phys. Res. A, Accel. Spectrom. Detect. Assoc. Equip.*, vol. 466, no. 1, pp. 168–173, 2001. doi: [10.1016/S0168-9002\(01\)00840-3](https://doi.org/10.1016/S0168-9002(01)00840-3).
- [23] G. Bertuccio, Prospect for energy resolving X-ray imaging with compound semiconductor pixel detectors, *Nucl. Instrum. Methods Phys. Res. A, Accel. Spectrom. Detect. Assoc. Equip.*, vol. 546, nos. 1–2, pp. 232–241, 2005. doi: [10.1016/j.nima.2005.03.015](https://doi.org/10.1016/j.nima.2005.03.015).
- [24] L. Abbene, S. Del Sordo, E. Caroli, G. Gerardi, G. Raso, S. Caccia, and G. Bertuccio, Hard X-ray response of pixellated CdZnTe detectors, *J. Appl. Phys.*, vol. 105, no. 12, 2009, Art. no. 124508. doi: [10.1063/1.3153161](https://doi.org/10.1063/1.3153161).
- [25] X. Lu, C. Liu, H. Jiang, X. Zou, A. Zhang, and K. M. Lau, Monolithic integration of enhancement-mode vertical driving transistor on a standard InGaP/GaN light emitting diode structure, *Appl. Phys. Lett.*, vol. 109, no. 5, 2016, Art. no. 053504. doi: [10.1063/1.4960105](https://doi.org/10.1063/1.4960105).
- [26] W. Shaobing, G. Jianfeng, W. Weibo, and Z. Junyun, W-band MMIC PA with ultrahigh power density in 100-nm AlGaP/GaN technology, *IEEE Trans. Electron. Devices*, vol. 63, no. 10, pp. 3882–3886, Oct. 2016. doi: [10.1109/TED.2016.2597244](https://doi.org/10.1109/TED.2016.2597244).
- [27] X. Lu, J. Ma, C. P. Yue, and K. M. Lau, A GaN-based lamb-wave oscillator on silicon for high-temperature integrated sensors, *IEEE Microw. Wireless Compon. Lett.*, vol. 23, no. 6, pp. 318–320, Jun. 2013. doi: [10.1109/LMWC.2013.2260734](https://doi.org/10.1109/LMWC.2013.2260734).
- [28] A. Pullia, G. Bertuccio, D. Maiocchi, S. Caccia, and F. Zocca, An SiC/GaN detector/front-end detection system for high-resolution alpha-particle spectroscopy, *IEEE Trans. Nucl. Sci.*, vol. 55, no. 6, pp. 3736–3740, Dec. 2008. doi: [10.1109/TNS.2008.2007722](https://doi.org/10.1109/TNS.2008.2007722).
- [29] X. Zhang, X. Zou, X. Lu, C. W. Tang, and K. M. Lau, Fully- and quasi-vertical GaN-on-Si p-i-n diodes: High performance and comprehensive comparison, *IEEE Trans. Electron. Devices*, vol. 64, no. 3, pp. 809–815, Mar. 2017. doi: [10.1109/TED.2017.2647990](https://doi.org/10.1109/TED.2017.2647990).
- [30] J.-Y. Duboz, E. Frayssinet, S. Chenot, J.-L. Reverchon, and M. Idir, X-ray detectors based on GaN Schottky diodes, *Appl. Phys. Lett.*, vol. 97, no. 16, 2010, Art. no. 163504. doi: [10.1063/1.3500838](https://doi.org/10.1063/1.3500838).
- [31] K. Fu, G. Yu, C. Yao, G. Wang, M. Lu, and G. Zhang, X-ray detectors based on Fe doped GaN photoconductors, *Phys. Status Solidi-Rapid Res. Lett.*, vol. 5, nos. 5–6, pp. 187–189, 2011. doi: [10.1002/pssr.201105163](https://doi.org/10.1002/pssr.201105163).
- [32] H. Wei, Y. Fang, P. Mulligan, W. Chuirazzi, H.-H. Fang, C. Wang, B. R. Ecker, Y. Gao, M. A. Loi, L. Cao, and J. Huang, Sensitive X-ray detectors made of methylammonium lead tribromide perovskite single crystals, *Nature Photon.*, vol. 10, pp. 333–339, May 2016. doi: [10.1038/NPHOTON.2016.41](https://doi.org/10.1038/NPHOTON.2016.41).